



AC A1430-B

UV-curable Epoxy Sealant for Rigid OLED Applications

PRODUCT DESCRIPTION:

- Base chemistry: epoxy only, cationic polymerization
- One component adhesive ready for use, solvent-free, UV curable, room temperature stable

PRODUCT USE:

- UV-curable epoxy OLED sealant

FEATURES:


- Epoxy only, high adhesion, high Tg, long shelf and working life, room temperature stable, not sensitive to oxygen in cure process, excellent reliability performances, robust for solder reflow process

INSTRUCTIONS FOR USE:

- 1) Clean the substrates to remove contamination, dust, moisture, salt and/or oil
- 2) Dispense adhesive on substrates
- 3) Bond substrates (with active alignment – optional)
- 4) UV cure to bond
- 5) Thermal post cure (optional)

TGA DATA:

Conditions: scan rate 10°C/min, in air

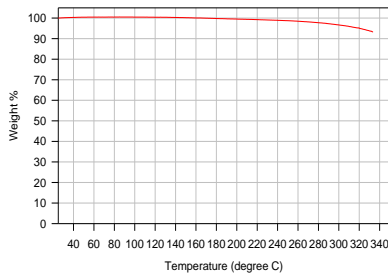

GENERAL USAGE INFORMATION:

Shipment: no restriction on shipment and no cold shipment is needed

Storage: After the adhesive is received in black syringes or amber HDPE bottles, room temperature storage (15-30°C) in the original container is required.

SAFETY AND HANDLING

The uncured adhesive can be cleaned from apparatus with isopropyl alcohol (IPA), methyl ethyl ketone (MEK), or commercial alcohol based cleaning solution. Avoid direct skin and eye contact. Use only in well ventilated areas. Use protective clothing, gloves and safety goggles. Read [Material Safety Data Sheet](#) before handling.

UV CURING CONDITIONS:

- UV Metal Halide or Mercury UV light source with UV-A (320-400 nm) with UV light intensity: 200 to 1,000 mW/ cm²
- LED-365 nm with UV light intensity: 100 to 1,000 mW/ cm²

LED-365 nm		Metal Halide/Mercury(UV-A: 320-400 nm)	
UV intensity (mW/cm ²)	time (sec)	UV intensity (mW/cm ²)	time (sec)
200	50 sec or more	200	40sec or more
or 300	35 sec or more	or 300	20 sec or more
or 400	25 sec or more	or 400	15 sec or more
or 500	20 sec or more	or 500	10 sec or more
or 1,000	10 sec or more	or 1,000	5 sec or more

- Thermal post cure at 80 to 100°C for 30 to 60 minutes will promote full cure and improve adhesion of bonded parts
- The recommended UV cure dose is at the adhesive. If the substrates absorb curing light, then the actual cure dose needs to be increased.

TYPICAL PROPERTIES

Uncured resin

Viscosity (cps, 25 °C)	>90,000
Density (g/mL)	1.1
Storage (°C)	15 – 25
Shelf life (15 - 25 °C)	6 months
Working life (15 - 25 °C)	3 months

Cured film

Outgas, weight % (125°C, 120 hr, air)	0.10
Outgas, weight % (per MIL-STD 883/5011)	0.19
Outgas, weight % (per Telcordia GR-1221)	0.13
Water absorption (% , 100 °C until saturation)	0.2
Water Transmission Rate (50 °C/95% RH, g/m ² 24hrs, ASTM E96-80)	3
Water permeability (g/m 24 hrs) (50 °C/95% RH, 75 µm film)	2 x 10 ⁻⁴
Shrinkage (linear, %)	< 0.3
Hardness – Shore D	94
Glass transition temperature (DMA, °C)	110
Dielectric Strength (estimated, kV/mm)	20-25
Coefficient of thermal expansion (DMA by compression), 4-5 mm thick sample	
below Tg (x10 ⁻⁶), °C ⁻¹	40
above Tg (x10 ⁻⁶), °C ⁻¹	110
Physical properties tested at 25°C, 50% RH (ASTM D638)	
Tensile strength, MPa	50
Elongation (%)	3
Young's Modulus, MPa	3,000